


NASA/TM-1998-206282



Compositional Effects on Electromechanical Degradation of RAINBOW Actuators

*David E. Dausch and Stephanie A. Wise
Langley Research Center, Hampton, Virginia*

January 1998

The NASA STI Program Office . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the lead center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA counter-part or peer-reviewed formal professional papers, but having less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.
- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or co-sponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that help round out the STI Program Office's diverse offerings include creating custom thesauri, building customized databases, organizing and publishing research results . . . even providing videos.

For more information about the NASA STI Program Office, see the following:

- Access the NASA STI Program Home Page at ***<http://www.sti.nasa.gov>***
- Email your question via the Internet to help@sti.nasa.gov
- Fax your question to the NASA Access Help Desk at (301) 621-0134
- Phone the NASA Access Help Desk at (301) 621-0390
- Write to:
NASA Access Help Desk
NASA Center for AeroSpace Information
800 Elkridge Landing Road
Linthicum Heights, MD 21090-2934

NASA/TM-1998-206282



Compositional Effects on Electromechanical Degradation of RAINBOW Actuators

*David E. Dausch and Stephanie A. Wise
Langley Research Center, Hampton, Virginia*

National Aeronautics and
Space Administration

Langley Research Center
Hampton, Virginia 23681-2199

January 1998

Acknowledgments

The authors gratefully acknowledge the contributions of Matthew Hooker of Lockheed Martin Engineering & Sciences, Hampton, Virginia.

The use of trademarks or names of manufacturers in this report is for accurate reporting and does not constitute an official endorsement, either expressed or implied, of such products or manufacturers by the National Aeronautics and Space Administration.

Available from the following:

NASA Center for AeroSpace Information (CASI)
800 Elkridge Landing Road
Linthicum Heights, MD 21090-2934
(301) 621-0390

National Technical Information Service (NTIS)
5285 Port Royal Road
Springfield, VA 22161-2171
(703) 487-4650

Abstract

The effect of ceramic composition on the electromechanical displacement degradation of RAINBOW (Reduced and Internally Biased Oxide Wafer) actuators was investigated. RAINBOWs were fabricated from commercially available PZT-5H and PZT-5A piezoelectric disks as well as from tape cast PLZT piezoelectric 7/65/35 and electrostrictive 9/65/35 compositions. Displacement properties were measured at low electric fields (10 to 13 kV/cm) under loads of 0 to 500 g, and displacement degradation as a function of time was observed over 10^7 cycles. The PZT-5A and PLZT 9/65/35 compositions exhibited minimal decrease in displacement when load was applied. Furthermore, these compositions retained approximately 65 percent of their initial displacement after 10^7 cycles under a load of 300 g. PZT-5H and PLZT 7/65/35 degraded completely under these conditions.

Introduction

High-displacement RAINBOW (Reduced and Internally Biased Oxide Wafer) actuators are receiving increased attention for applications requiring high strain such as noise cancellation, optical positioning, active structural control, and sonar (refs. 1 through 3). These devices are capable of producing unimorph-type bending with single element displacements greater than 1 mm under moderate loads (ref. 3). RAINBOWs are fabricated by chemically reducing, or selectively removing oxygen from, one side of a conventional high-lead-containing piezoelectric or electrostrictive ceramic disk such as PZT (lead zirconate titanate). This process transforms the ceramic into a monolithic domed structure containing a highly metallic layer and a piezoelectric oxide layer. When activated by an electric field, the stress-biased wafer exhibits amplified axial displacements. One target application for RAINBOW devices is a solid-state actuating mechanism to replace mechanical motors for optical positioning in space-borne spectrometers (ref. 4). Such an application would require repeatable displacement properties while operating below 1 Hz for 10 million cycles under moderate applied load.

The use of RAINBOWs in applications that require long device lifetimes necessitates assessment of the long-term reliability of these materials. Ferroelectric polarization fatigue in piezoelectric and electrostrictive RAINBOWs has been investigated and compared with fatigue in conventional ceramics over 10^8 cycles (ref. 5). Ferroelectric fatigue is the degradation of the nonlinear electrical properties caused by repeated cycling at high electric fields (i.e., greater than 20 kV/cm). Typical actuator devices, however, would not be driven by such large fields. In order to characterize these materials under conditions which better emulate actuator applications, the electromechanical displacement properties of RAINBOWs activated by low ac (alternating current) fields were observed. The objective of this investigation was to examine the effects of the starting ceramic composition on the electromechanical displacement degrada-

tion of these materials. RAINBOWs were fabricated from commercially available PZT wafers as well as tape cast PLZT (lanthanum-modified PZT) ceramics. Actuator displacements were measured under static loads of 0 to 500 g, and degradation in the displacement properties over time, or displacement fatigue, was characterized for up to 10^7 cycles.

Experimental Procedure

PLZT piezoelectric 7/65/35 (65/35 Zr/Ti ratio with 7 percent La dopant by weight) and PLZT electrostrictive 9/65/35 ceramics were produced by tape casting for RAINBOW fabrication. Powder for tape casting was synthesized at 900°C from mixed oxides of lead, lanthanum, zirconium, and titanium. Ball-milled powder was then combined with a resin solution (Ferro UN1866 resin) and cast into thin sheets (approximately 500 μm when dried) on a Du Pont Teflon surface. Circular disks were punched from the dried tapes and sintered at 1275°C on PbZrO₃ powder beds. Use of the beds provided a sintering atmosphere which was rich in PbO to minimize PbO loss from the ceramics. The fired ceramics were 300 to 360 μm (12 to 14 mils) in thickness and 22.2 mm (7/8 in.) in diameter. RAINBOWs were also fabricated from commercially available PZT-5A and PZT-5H piezoelectric disks. These disks were 25.4 mm (1 in.) in diameter and 380 μm (15 mils) in thickness. The piezoelectric and electrostrictive ceramics were chemically reduced by placing the oxide ceramic disks on graphite blocks in a furnace at 975°C for approximately 1 hour to form the oxide and metal layered structure. The remaining oxide layer comprised approximately 50 to 60 percent of the total thickness of each RAINBOW. After quenching the RAINBOWs to room temperature, silver epoxy electrodes were applied to both surfaces. RAINBOWs with electrodes were poled at room temperature with a dc (direct current) bias of 400 to 500 V.

Electromechanical degradation was measured by applying ac electric fields of ± 6.5 kV/cm (± 16.5 V/mil) to the commercial piezoelectric compositions, ± 5 kV/cm

(± 12.5 V/mil) to the piezoelectric PLZT 7/65/35 composition, and 10 kV/cm (25 V/mil) unipolar (i.e., 0 to 10 kV/cm) to the 9/65/35 electrostrictors. These low electric fields were chosen to ensure that each composition produced displacements in their respective linear ranges. Electrostrictors were driven with unipolar voltage since both positive and negative voltages produced equal displacements in the same direction. Because the chemically reduced layers had low electrical resistance (less than 1 Ω), electric fields were calculated by assuming that the voltage was dropped only across the oxide layers. Electromechanical displacements under loads of 0 to 500 g were measured at a frequency of 1 Hz. Displacements were sensed with linear variable displacement transducers (LVDT), and static point loads were applied by placing known weights on the LVDT rod which rested on the top surface of the RAINBOW. Displacement fatigue was measured at a frequency of 20 Hz for 10^7 cycles under loads of both 0 and 300 g. The fatigued samples were repoled, and displacements were immediately measured again at 20 Hz.

Results

Effect of Static Load on Displacement

Displacement (D) values under loads of 0 and 500 g as well as the percentage change in displacement with applied load are listed in table 1. These values represent an average of five samples per composition. Higher free (no load) displacement was observed for the commercial piezoelectric compositions than for PLZT 7/65/35. For PZT-5A, displacement decreased by only 2 percent when a load of 500 g was applied as compared with a 20- and 34-percent decrease for the two other piezoelectrics. Electrostrictive PLZT 9/65/35 exhibited the highest overall displacement and best load-bearing capability of all the RAINBOW compositions tested.

The normalized displacement properties of RAINBOWs under loads of 0 to 500 g are shown in figure 1 and indicate the relative dependence of displacement on applied load for each composition. As shown, piezoelectric PZT-5H and PLZT 7/65/35 exhibited

Table 1. Average Displacements (D) of Unloaded and Loaded RAINBOWs

RAINBOW composition	D_{0g} , μm	D_{500g} , μm	ΔD_{0-500g} , percent
PZT-5H ^a	83	66	-20
PZT-5A ^a	88	86	-2
PLZT 7/65/35 ^b	55	36	-34
PLZT 9/65/35 ^c	116	117	+1

^aPeak-to-peak displacements at ± 6.5 kV/cm and 1 Hz.

^bPeak-to-peak displacements at ± 5 kV/cm and 1 Hz.

^cPeak-to-peak displacements at 10 kV/cm (unipolar) and 1 Hz.

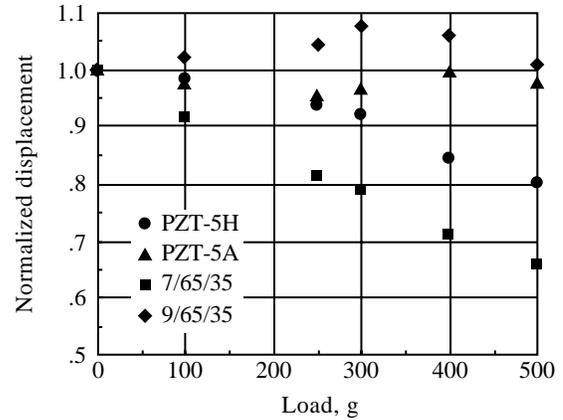


Figure 1. Change in displacement with various static loads. Field levels were 10 kV/cm unipolar for electrostrictive 9/65/35, ± 5 kV/cm for piezoelectric 7/65/35, and ± 6.5 kV/cm for commercial piezoelectric compositions at 1 Hz.

continuously decreasing displacements with increasing load. PZT-5A displacement values under all test loads were no more than 5 percent lower than the initial free displacement for this composition. The displacement of the electrostrictive composition actually increased by as much as 8 percent under a load of 300 g compared with the properties under no load.

Low-Field Displacement Fatigue

Degradation in the displacement properties as a function of time was investigated for RAINBOW actuators to determine the characteristics of these devices over long lifetimes. Table 2 is a summary of the displacement fatigue characteristics including fraction of initial displacement remaining after 10^7 cycles (fatigued) and fraction of initial displacement recovered after repoling under loads of 0 and 300 g. Displacement fatigue is shown for PZT-5H, PZT-5A, PLZT 7/65/35, and PLZT 9/65/35 RAINBOWs in figures 2, 3, 4, and 5, respectively.

Table 2. Fractions of Initial Displacement for Unloaded and Loaded RAINBOWs

RAINBOW composition	Voltage conditions same as in table 1 except at 20 Hz; fatigued data obtained after 10^7 cycles unless otherwise noted			
	No load		Load of 300 g	
	Fatigued	Repoled	Fatigued	Repoled
PZT-5H	0.91	1.03	^a 0.06	0.83
PZT-5A	0.92	1.00	0.63	0.94
PLZT 7/65/35	0.78	1.01	^b 0.05	0.05
PLZT 9/65/35	0.80	0.81	0.65	0.63

^aAfter 2×10^4 cycles.

^bAfter 2×10^3 cycles.

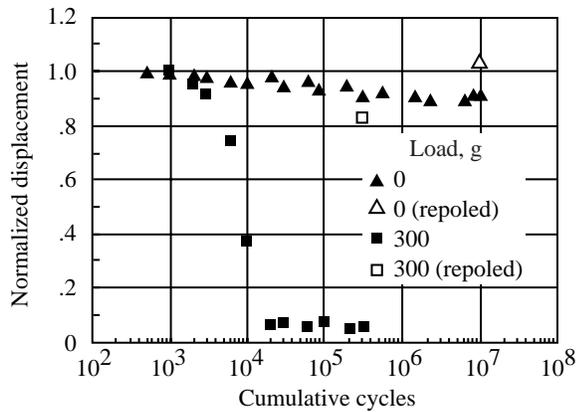


Figure 2. Displacement fatigue of PZT-5H RAINBOWs with applied loads of 0 and 300 g measured at ± 6.5 kV/cm and 20 Hz.

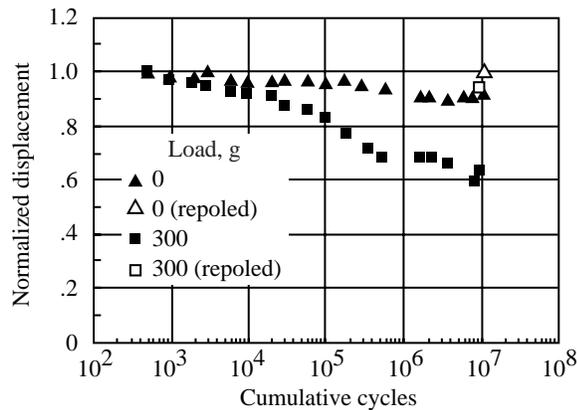


Figure 3. Displacement fatigue of PZT-5A RAINBOWs with applied loads of 0 and 300 g measured at ± 6.5 kV/cm and 20 Hz.

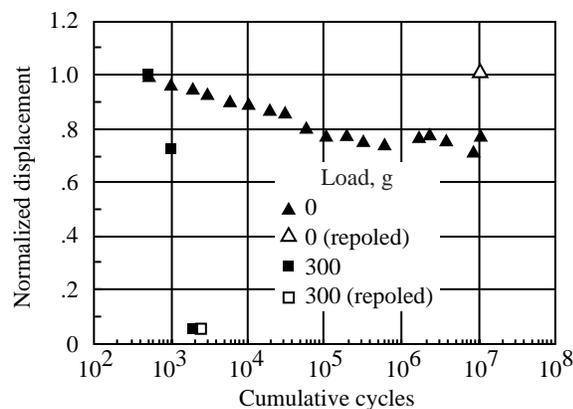


Figure 4. Displacement fatigue of PLZT 7/65/35 RAINBOWs with applied loads of 0 and 300 g measured at ± 5 kV/cm and 20 Hz.

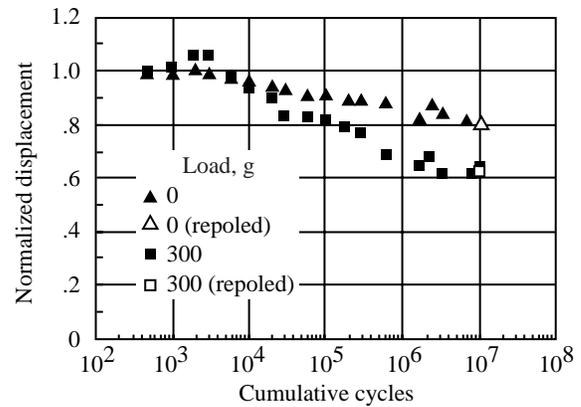


Figure 5. Displacement fatigue of PLZT 9/65/35 RAINBOWs with applied loads of 0 and 300 g measured at 10 kV/cm unipolar and 20 Hz.

The commercial piezoelectric compositions provided the most resistance to displacement fatigue over 10^7 cycles with no load. A displacement degradation of less than 10 percent was observed. However, PZT-5A with its greater load-bearing capability fatigued much less than PZT-5H with an applied load of 300 g. PZT-5H was completely fatigued, that is, 94 percent loss in displacement, after 2×10^4 cycles. When repoled after the fatigue measurements, the original free displacement properties were completely restored for both compositions, whereas 83 to 94 percent of the initial displacement was recovered when repoled under a load of 300 g. This finding reveals that the properties of these materials can be replenished by periodically applying a dc bias (repoling) to the samples during their lifetimes. It is unknown how many dc bias applications can be successfully employed. Consequently, for applications where a load must be considered, the PZT-5A composition would be the most desirable.

Both PLZT 7/65/35 and 9/65/35 RAINBOWs exhibited approximately 20 percent displacement fatigue when no load was applied. The initial higher displacement obtained prior to the fatigue test for the piezoelectric 7/65/35 RAINBOW was recovered by repoling; however, the properties of the electrostrictive 9/65/35 composition were unaffected by repoling. Superior load-bearing capability was evident in the 9/65/35 composition, as 7/65/35 completely fatigued after only 2×10^3 cycles and 9/65/35 retained 65 percent of its original displacement after 10^7 cycles. The initial displacements could not be recovered for either of these compositions when repoled after the fatigue measurement under a load of 300 g.

As shown, composition of the starting ceramic has a large effect on the lifetime and reliability of RAINBOW

actuators. Because most applications would require some load-bearing capability, PZT-5A and PLZT 9/65/35 would be the most useful of the four compositions investigated. These compositions continued to retain greater than 60 percent of their initial displacements after 10^7 cycles under applied load. PZT-5A could retain on the order of 90 percent of its initial displacement values with periodically applied dc bias. For an optical positioning mechanism operating at 0.25 Hz, a lifetime of 10^7 cycles for PZT-5A or PLZT 9/65/35 would be equivalent to greater than 11000 hours of continuous operation. In contrast, PZT-5H and PLZT 7/65/35 under applied load would function continuously for only 22 (2×10^4 cycles) or 2 (2×10^3 cycles) hours, respectively, without periodic repoling.

Summary of Results

Electromechanical degradation was investigated for PZT-based RAINBOW actuators fabricated from piezoelectric PZT-5H, PZT-5A, and PLZT 7/65/35 as well as electrostrictive PLZT 9/65/35 ceramics. Composition had a significant effect on the electromechanical properties. Specific results were as follows:

1. The PZT-5A and PLZT 9/65/35 compositions provided the greatest load-bearing capability. Minimal decrease in displacement was observed for these compositions with static loads of 500 g, whereas the PZT-5H and PLZT 7/65/35 compositions exhibited decreases of 20 and 34 percent, respectively.
2. The commercial PZT piezoelectric compositions exhibited the lowest decrease in free displacement over 10^7 cycles (i.e., less than 10 percent), whereas the properties of the tape cast PLZT RAINBOWs diminished by approximately 20 percent. Repoling the three piezoelectric RAINBOWs after the no load fatigue measurement restored displacements to their initial values. Electrostrictive displacement properties could not be restored by repoling.
3. The PZT-5A and PLZT 9/65/35 compositions retained approximately 65 percent of their initial displacement when a load of 300 g was applied for 10^7 cycles. Additionally, PZT-5A displacement was restored to 94 percent of the initial value by repoling after the fatigue measurement. The PZT-5H and PLZT 7/65/35 compositions possessed relatively short lifetimes (less than 2×10^4 cycles) with applied load. These results indicated that for optical positioning applications, the PZT-5A and PLZT 9/65/35 compositions would provide greater electromechanical repeatability.

NASA Langley Research Center
Hampton, VA 23681-2199
December 16, 1997

References

1. Haertling, Gene H.: Chemically Reduced PLZT Ceramics for Ultra-High Displacement Actuators. *Ferroelectrics*, vol. 154, 1994, pp. 101–106.
2. Sherrit, S.; Wiederick, H. D.; Mukherjee, B. K.; and Haertling, G. H.: The Dielectric, Piezoelectric and Hydrostatic Properties of PLZT Based Rainbow Ceramics. *Proceedings of the Ninth IEEE International Symposium on Applications of Ferroelectrics—ISAF '94*, R. K. Pandey, Michael Liu, and Ahmad Safar, eds., IEEE, 1994, pp. 390–393.
3. Haertling, Gene H.: Rainbow Ceramics—A New Type of Ultra-High-Displacement Actuator. *American Ceram. Soc. Bull.*, vol. 73, no. 1, Jan. 1994, pp. 93–96.
4. Wise, Stephanie A.; Hardy, Robin C.; and Dausch, David E.: Design and Development of an Optical Path Difference Scan Mechanism for Fourier Transform Spectrometers Using High Displacement RAINBOW Actuators. *Proceedings of the 1997 SPIE Smart Structures and Materials Conference—Industrial and Commercial Applications of Smart Structures Technologies*, Janet M. Sater, ed., Volume 3044, SPIE, 1997, pp. 342–349.
5. Dausch, David E.: Ferroelectric Polarization Fatigue in PZT-Based RAINBOWs and Bulk Ceramics. *J. American Ceram. Soc.*, vol. 80, no. 9, 1997, pp. 2355–2360.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)	2. REPORT DATE January 1998	3. REPORT TYPE AND DATES COVERED Technical Memorandum		
4. TITLE AND SUBTITLE Compositional Effects on Electromechanical Degradation of RAINBOW Actuators		5. FUNDING NUMBERS WU 505-63-50-20		
6. AUTHOR(S) David E. Dausch and Stephanie A. Wise				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) NASA Langley Research Center Hampton, VA 23681-2199		8. PERFORMING ORGANIZATION REPORT NUMBER L-17629		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001		10. SPONSORING/MONITORING AGENCY REPORT NUMBER NASA/TM-1998-206282		
11. SUPPLEMENTARY NOTES Dausch: NRC-NASA Resident Research Associate at the Langley Research Center, Hampton, VA; Wise: Langley Research Center, Hampton, VA.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified-Unlimited Subject Category 76 Availability: NASA CASI (301) 621-0390		12b. DISTRIBUTION CODE		
13. ABSTRACT (Maximum 200 words) The effect of ceramic composition on the electromechanical displacement degradation of RAINBOW (Reduced and Internally Biased Oxide Wafer) actuators was investigated. RAINBOWs were fabricated from commercially available PZT-5H and PZT-5A piezoelectric disks as well as from tape cast PLZT piezoelectric 7/65/35 and electrostrictive 9/65/35 compositions. Displacement properties were measured at low electric fields (10 to 13 kV/cm) under loads of 0 to 500 g, and displacement degradation as a function of time was observed over 10 ⁷ cycles. The PZT-5A and PLZT 9/65/35 compositions exhibited minimal decrease in displacement when load was applied. Furthermore, these compositions retained approximately 65 percent of their initial displacement after 10 ⁷ cycles under a load of 300 g. PZT-5H and PLZT 7/65/35 degraded completely under these conditions.				
14. SUBJECT TERMS Piezoelectric actuators; Displacement properties; Electromechanical fatigue			15. NUMBER OF PAGES 9	
			16. PRICE CODE A02	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT	